


Production Code	SYP-100X	Issued	2025-11-11
Type of Product	Silane crosslinkable Polyethylene, XLPE for low voltage cables	Rev.	0
Main Application	Insulation of power, control and instrument cables - scorch & extrusion stability		
Related Standard	IEC 60502-1		

Description SYP-100X is a silane-crosslinked PE. It is a compound with improved long-term extrudability and optimized properties for high-speed extrusion operations, and has basic UV resistance and moisture crosslinking properties.

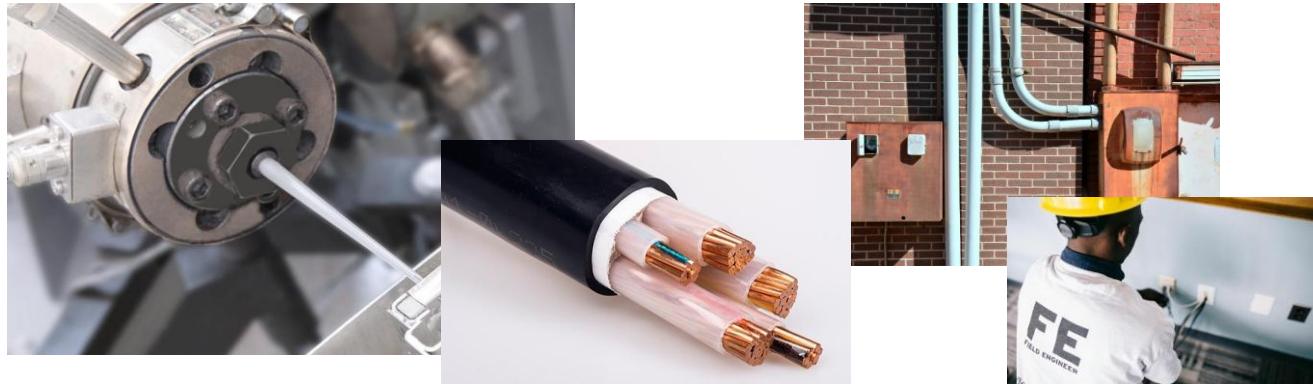

Property	Unit	Specification	Typical Value	Test method
Physical properties				
Specific gravity	-	-	0.928	ASTM D 792
Tensile strength [Min.]	N/mm ²	12.5	28.9	IEC 60811-501
Elongation at break [Min.]	%	200	748	IEC 60811-501
Thermal property				
Aging condition - 136°C/168hrs				
Tensile strength after aging - Variation [Max.]	%	±25	+9	IEC 60811-401
Elongation at break after aging - Variation [Max.]	%	±25	-7	IEC 60811-401
Cross-linking property				
Test condition - Hot: 200°C, 20N/cm² load, 10min Set: after cooling				
Hot elongation under high temperature [Max.]	%	175	65	IEC 60811-507
Set deformation after cooling [Max.]	%	15	0	IEC 60811-507
Electrical property				
Volume resistivity - Thickness 1mm [Min.]	Ω·m	1.00E+16	1.26E+17	ASTM D 257
Rheological property				
MI (Melt flow index) - 190°C/2.16kgf [Min.]	g/10min	-	2.6	ASTM D 1238
Environmental regulation				
RoHS I - Analysis by XRF				
Material	Pb	Cd	Cr(6+)	Hg
Content (PPM)	Not detected	Not detected	Not detected	Not detected
PBBs				PBDEs
Content (PPM)	Not detected	Not detected	Not detected	Not detected

Package

Unit packing size - Available	25kg	500kg	1,000kg	Special weight - ()kg
Packing material	PP bag	PP bag with PE inner film	PP bag with Al inner film	Octagon Box with Al inner film
Suggestion of storage condition	This compound should be stored in a place away from direct sunlight and moisture, to prevent damage to the packaging, and it is recommended to store it in a place where the ambient temperature does not exceed 40°C.			
Shelf life of compound	The recommended storage period for products sealed in aluminum packaging is up to 12 months. However, the product's shelf life may vary depending on storage conditions.			

Proposed extrusion conditions

Preheating method	It is recommended that the material be preheated to 60°C/4hrs prior to extrusion. Preheating is essential to remove residual moisture and to enhance the stability of material flow during the extrusion process.
Additional M/B - Color, Catalyst, FR...	When using Color M/B, the addition level should be kept below 3%. Excessive loading may adversely affect the crosslinking properties.
Recommended extruder	A 90 mm single-screw extruder (compatible with 80 to 120 mm diameters), equipped with either a full-flight screw or a barrier mixing (BM) screw
Screw information (L/D, C/R)	L/D ratio: 25:1 (recommended range: 24:1 to 30:1) Compression ratio (C/R): 2.5:1 (suggested range: 2.0:1 to 3.0:1)
Miscellaneous	Remaining XLPE materials should be properly sealed and stored after use, as XLPE is highly sensitive to atmospheric moisture, potentially causing surface quality defects.

Temperature profile / 80mm extruder

Unit: °C

Cylinder 1	Cylinder 2	Cylinder 3	Cylinder 4	Neck	Head	Die
160±5	175±5	190±5	200±5	210±5	210±5	Gas torch allowed

* The temperatures listed above are typical processing conditions and may require adjustment depending on the extruder and screw specifications.

Remark

Key features	Process stability, Continuous extrusion, Long-term thermal stability, Moisture crosslinking
Advanced features	Smooth surface, Better flexible, Low die build-up